

The origin of the condensation energy scaling of Iron-based superconductors

YUNKYU BANG

Department of Physics, Chonnam National University, Kwangju 500-757, Republic of Korea

PACS 74.20.-z – Theories and models of superconducting state
 PACS 74.25.Bt – Thermodynamic properties
 PACS 74.70.Xa – Pnictides and chalcogenides

Abstract – The relation between the condensation energy (CE) and T_c of a phase transition reveals a fundamental nature of the transition. In view of this, the recent experimental observation of the non-BCS scaling relation of the CE *vs.* T_c ($\Delta E \sim T_c^{3.5}$) with about forty different samples of the Fe-based superconductors [J. Xing *et al.*, Phys. Rev. B 89, 140503 (2014)] was intriguing and strongly hinted at a non-BCS pairing mechanism. In this paper, we have studied the CE and T_c of the multiband BCS model and found that the observed anomalous scaling relation $\Delta E \sim T_c^{3.5}$ is well reproduced by the two-band BCS model paired by a dominant *repulsive interband interaction* ($V_{inter} > V_{intra} > 0$). Our result implies that this seemingly non-BCS-like scaling behavior of $\Delta E \sim T_c^{3.5}$, on the contrary to the common expectations, is in fact a strong experimental evidence that the pairing mechanism of the Fe-based superconductors is genuinely a BCS mechanism, meaning that *the Cooper pairs are formed by the itinerant carriers glued by a pairing interaction.*

Introduction. – The condensation energy (CE) ΔE of a superconductor is defined as the energy difference between the normal state and the superconducting (SC) state of the same system. The size of the CE is a measure of how much stable the SC state is, compared to the normal state, hence the CE is naturally related to the transition temperature T_c . In more fundamental context, the specific relation between the CE and the transition temperature T_c of a phase transition reveals the generic characteristics of the phase transition. For example, the magnetic transition with local moments such as a classic limit of Heisenberg model and Ising model has the relation $\Delta E_{mag} \propto T_c$, while the BCS theory of the one band superconductor predicts $\Delta E_{BCS} \propto T_c^2$ [1].

These different power law relations are rooted to the fact that the magnetic ordering above mentioned consists of local moments, while the BCS SC ordering consists of itinerant electrons. In a more revealing aspect, the former transition is determined solely by the potential energy (PE) gain $\Delta PE < 0$ by the ordering of the local moments without kinetic energy involved. On the other hand, the latter transition is determined by the subtle balance between the kinetic energy (KE) loss $\Delta KE > 0$ and the potential energy gain $\Delta PE < 0$ by the SC ordering. Therefore, the standard scaling law $\Delta E \propto T_c^2$ of the BCS

superconductor in fact reveals the fundamental nature of the transition that the SC condensation is formed by itinerant fermions.

In view of this observation, the recent report by J. Xing *et al.* [2] of $\Delta E \propto T_c^\beta$ ($\beta \approx 3.5$) with various Fe-based superconductors (IBS) is very intriguing and should contain the crucial information of the SC pairing mechanism. For example, the authors of [2] interpreted that this anomalous scaling relation is a strong evidence that the Fe-based superconductivity occur around the quantum criticality (QC) [3] and its pairing mechanism should be fundamentally different from the BCS pairing mechanism. On the other hand, regardless of the specific pairing mechanism, an extension of our general discussion above leads us to speculate that *the superconductivity of the IBS should have more itinerant (kinetic) character than the standard one band BCS superconductors.* We will show that this naive speculation is indeed correct and we do not need to invoke the QC to understand the anomalous scaling behavior of CE *vs.* T_c .

In this paper, we studied the CE and T_c of a minimal two band BCS model with various doping. To our surprise, this simple model immediately produced the relation $\Delta E \propto T_c^3$, which is a generic feature of the two band BCS superconductor mediated by a dominant interband

pairing interaction (i.e. $|V_{inter}| > |V_{intra}|$). Then the observed power $\beta \sim 3.5$ [2] can be easily obtained by adding a small amount of pair-breaking impurities.

Although we cannot completely rule out other theoretical explanations, our successful explanation of the anomalous scaling relation of the CE *vs.* T_c ($\Delta E \sim T_c^{3.5}$ [2]), combined with the recent successful explanation [4] of the another anomalous scaling relation of the specific heat jump ΔC *vs.* T_c (BNC scaling $\Delta C \sim T_c^3$) [5–13] using the same two band BCS model, has made a very strong case that *the pairing mechanism of the IBS is genuinely a BCS theory, with the multi-bands, mediated by a dominant inter-band pairing interaction.* The strong correlation effects certainly should exist in these compounds in normal state, such as to renormalize the quasiparticle masses m_{qp}^* and the pairing interactions $V_{ab}(\mathbf{q})$, etc. However, the SC pairing mechanism itself seems to be governed by the BCS theory.

Condensation Energy. –

Two Band BCS model. In real compounds of the IBS, there exist multiple hole and multiple electron bands. In our minimal two band model, each hole and electron band $\xi_{h(e)}(k)$, their DOS $N_{h(e)}$, and the gap functions $\Delta_{h(e)}$ represent a group of hole bands and a group of electron bands, respectively [4, 14]. The Hamiltonian for the two band superconductor is written as

$$\begin{aligned} H = & \sum_{k,\sigma} \xi_h(k) h_{k,\sigma}^\dagger h_{k,\sigma} + \sum_{k,\sigma} \xi_e(k) e_{k,\sigma}^\dagger e_{k,\sigma} \\ & + \sum_{k,k'} V_{hh} h_{k,\uparrow}^\dagger h_{-k,\downarrow}^\dagger h_{k',\downarrow} h_{-k',\uparrow} + \sum_{k,k'} V_{ee} e_{k,\uparrow}^\dagger e_{-k,\downarrow}^\dagger e_{k',\downarrow} e_{-k',\uparrow} \\ & + \sum_{k,k'} V_{he} h_{k,\uparrow}^\dagger h_{-k,\downarrow}^\dagger e_{k',\downarrow} e_{-k',\uparrow} + \sum_{k,k'} V_{eh} e_{k,\uparrow}^\dagger e_{-k,\downarrow}^\dagger h_{k',\downarrow} h_{-k',\uparrow} \end{aligned} \quad (1) \text{with}$$

where $V_{ab} = \langle V_{ab}(k, k') \rangle_{FS}$ is Fermi surface (FS) averaged pairing potentials with $a, b = h, e$ and assumed to have a BCS cut-off, i.e. $|\xi_{h,e}(k)| < \Lambda_{hi}$ (which is possibly the characteristic spin-fluctuation frequency, ω_{sf} , in Fe-based superconductors).

It is straightforward to extend the standard BCS theory to calculate the CE of the multi-band superconductor. Assuming the SC order parameters (OPs) Δ_h and Δ_e , the above Hamiltonian is written in a quadratic form as follows,

$$\begin{aligned} H = & 2 \sum_k \xi_h(k) h_k^\dagger h_k + 2 \sum_k \xi_e(k) e_k^\dagger e_k \\ & + \sum_k \Delta_h h_k^\dagger h_{-k}^\dagger + \sum_k \Delta_h^* h_k h_{-k} \\ & + \sum_k \Delta_e e_k^\dagger e_{-k}^\dagger + \sum_k \Delta_e^* e_k e_{-k} \end{aligned} \quad (2)$$

where 2 is due to the spin degree of freedom (d.o.f.) and

the self-consistent gap equations are defined as

$$\begin{aligned} \Delta_h &= - \sum_k V_{hh} b_k^h - \sum_k V_{he} b_k^e \\ \Delta_e &= - \sum_k V_{eh} b_k^h - \sum_k V_{ee} b_k^e \end{aligned} \quad (3)$$

with the Cooper pair amplitudes $b_k^h = \langle h_{k\uparrow} h_{-k\downarrow} \rangle$ and $b_k^e = \langle e_{k\uparrow} e_{-k\downarrow} \rangle$, respectively. It is convenient to introduce the momentum summed Cooper pair amplitudes $b^{h(e)} = \sum_k b_k^{h(e)} = \sum_k \frac{1}{2} \frac{\Delta_{h(e)}}{\sqrt{\xi_{h(e)}^2(k) + \Delta_{h(e)}^2}} =$

$N_{h(e)} \Delta_{h(e)} \log \frac{\Lambda_{hi} + \sqrt{\Lambda_{hi}^2 + \Delta_{h(e)}^2}}{|\Delta_{h(e)}|}$ at $T = 0$. Unlike the single band gap equation, Eq.(3) shows that the OPs $\Delta_{h(e)}$ and the Cooper pair amplitudes $b^{h(e)}$ are coupled through 2×2 matrix $\hat{V}_{ab}$ such as $\Delta_a = -\hat{V}_{ab} \cdot b^b$. Once we solve $\Delta_{h(e)}$ from the coupled gap equations Eq.(3), we numerically solve the inverse matrix equation to obtain $b^{h(e)}$, with which $\langle H \rangle_s$ of the two-band Hamiltonian Eq.(2) is straightforwardly calculated. With the general matrix equation $\Delta_a = -\hat{V}_{ab} \cdot b^b$, there is no simple expression for $\langle H \rangle_s$ as in one band BCS superconductor [15] except two special cases: (A) $V_{he} = V_{eh} = 0$, and (B) $V_{hh} = V_{ee} = 0$.

The case (A) is a trivially decoupled two single band superconductors with two independent T_c s and $\Delta_{h,e}$, respectively, for each band, that is not our interest. The case (B) is more interesting case that is the pure inter-band pairing limit and the analytic form of the CE ΔE can be worked out as follows,

$$\begin{aligned} \Delta E &= \langle H \rangle_s - \langle H \rangle_n \\ &= \Delta KE + \Delta PE \end{aligned} \quad (4)$$

$$\Delta KE = \sum_{a=h,e} \sum_k \left[|\xi_a(k)| - \frac{\xi_a^2(k)}{E_a(k)} \right] \quad (5)$$

$$\Delta PE = V_{he} b^{*h} b^e + V_{eh} b^{*e} b^h, \quad (6)$$

where $E_{h(e)}(k) = \sqrt{\xi_{h(e)}^2(k) + \Delta_{h(e)}^2}$. The kinetic energy part $\Delta KE = \Delta KE_h + \Delta KE_e$ is calculated in the same manner as in the single band model as [15]

$$\Delta KE_{h(e)} = -\frac{1}{2} N_{h(e)} \Delta_{h(e)}^2 + \left| \frac{\Delta_h \Delta_e}{V_{he}} \right| \quad (7)$$

where we use the fact $V_{he} = V_{eh}$. The potential energy part Eq.(6) is

$$\Delta PE = \frac{\Delta_h^* \Delta_e}{V_{he}} + \frac{\Delta_e^* \Delta_h}{V_{eh}} = 2 \frac{\Delta_h \Delta_e}{V_{he}} \quad (8)$$

where we assume $\Delta_{h(e)}^* = \Delta_{h(e)}$. Therefore when $V_{he} > 0$ (repulsive) and the OPs $\Delta_{h(e)}$ have the opposite signs each other, or when $V_{he} < 0$ (attractive) and the OPs

$\Delta_{h(e)}$ have the same signs each other, we finally obtain the following simple expression

$$\Delta E = -\frac{1}{2}N_h\Delta_h^2 - \frac{1}{2}N_e\Delta_e^2. \quad (9)$$

The result of the total CE in Eq.(9) looks quite natural as the sum of the single band BCS CE of each band. However, this natural looking expression is totally disguising because the $\Delta KE_{h(e)}$ and $\Delta PE_{h(e)}$ of each band maximally depend on the other band with $V_{inter} \neq 0$ and $V_{intra} = 0$ (see Eq.(7) and (8)). As a consequence, the total CE ΔE of Eq.(9) will not follow the standard BCS scaling form ($\Delta E_{BCS} \sim \Delta_0^2 \sim T_c^2$), but will produce a non-trivial power-law relation because of the inverse relation $\frac{\Delta_h}{\Delta_e} \sim \frac{N_e}{N_h}$ (at $T = 0$) [14] and the T_c -formula $T_c \sim \exp[-1/(V_{inter}\sqrt{N_h N_e})]$ [4] of the two band BCS model mediated by the inter-band pairing interaction.

For general case when all $V_{ab} \neq 0$ ($a, b = h, e$), the ΔKE (Eq.(5)) can still be written as the following general expression

$$\Delta KE = \sum_{a=h,e} -\frac{1}{2}N_a\Delta_a^2 + N_i\Delta_a^2 \log \frac{\Lambda_{hi} + \sqrt{\Lambda_{hi}^2 + \Delta_a^2}}{|\Delta_a|}, \quad (10)$$

but the second term now cannot be reduced to the simple expression $|\frac{\Delta_h\Delta_e}{V_{he}}|$ as in Eq.(7). Also the ΔPE now contains more terms than Eq.(6) as

$$\Delta PE = V_{hh}b^{*h}b^h + V_{ee}b^{*e}b^e + V_{he}b^{*h}b^e + V_{eh}b^{*e}b^h, \quad (11)$$

and apparently ΔPE cannot have the simple expression as Eq.(8). Therefore total CE ΔE and T_c should be calculated numerically.

Modeling of Doping. To make a direct comparison with the experimental data of ΔE vs. T_c of the IBS [2], which are the collection of data of various iron Pnictides and chalcogenide (FePn/Ch) SC compounds with systematic doping by holes or electrons, we need a modeling of doping. Specifically, we are modeling the cases of $(\text{Ba}_{1-x}\text{K}_x)\text{Fe}_2\text{As}_2$ and $\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)_2\text{As}_2$ which have the most systematic doings in the experimental data. We first note that the undoped parent compound BaFe_2As_2 is a compensated metal, hence has the same number of electrons and holes, i.e. $n_h = n_e$. Therefore it is a reasonable approximation to assume $N_h \approx N_e$ at no doping and then the doping of holes (K, Na, etc.) or electrons (Co, Ni, etc.) is simulated by varying N_h and N_e while keeping $N_e + N_h = N_{tot} = \text{const.}$ Admittedly this modeling of doping is much too simple. However this assumption is qualitatively consistent with the Angle-Resolved-Photo-Emission-Spectroscopy (ARPES) measurements of $(\text{Ba}_{1-x}\text{K}_x)\text{Fe}_2\text{As}_2$ [16] and $\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)_2\text{As}_2$ [17] which show the systematic changes of hole (electron) FS sizes with dopings. Furthermore, the assumption $N_{tot} = \text{const.}$ is only for convenience and can be relaxed. The sensitive parameter of our model is the relative sizes between N_e

and N_h , but not the total DOS N_{tot} . Finally, it is not necessary to know the exact relation between the actual doping concentration "x" of real compounds and the values of $N_{h(e)}$ in our two-band model. When we plot our calculation results of $\Delta E(N_{h(e)})$ vs. $T_c(N_{h(e)})$, the explicit values of $N_{h(e)}$ become hidden parameters and we only extract the scaling relation between ΔE and T_c .

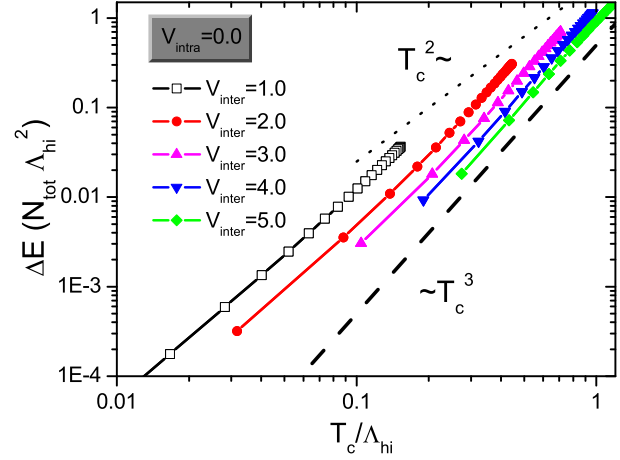


Fig. 1: (Color online) Numerical calculations of ΔE vs. T_c of the two band model with $\bar{V}_{intra} (= N_{tot}V_{intra}) = 0.0$ for $\bar{V}_{inter} (= N_{tot}V_{inter}) = 1.0, 2.0, 3.0, 4.0$ and 5.0 , respectively. The dotted line ($\sim T_c^2$, BCS scaling) and the dashed line ($\sim T_c^3$) are guides for the eyes.

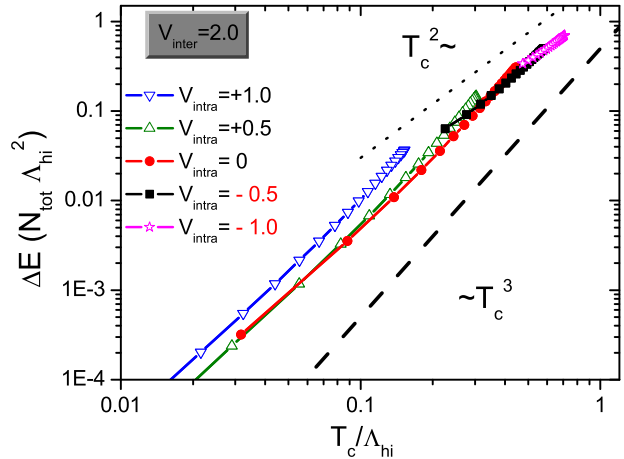


Fig. 2: (Color online) Numerical calculations of ΔE vs. T_c of the two band model with $\bar{V}_{inter} = 2.0$ for $\bar{V}_{intra} = +1.0, +0.5, 0.0, -0.5$ and -1.0 , respectively. The dotted line ($\sim T_c^2$, BCS scaling) and the dashed line ($\sim T_c^3$) are guides for the eyes.

Numerical results. — In all our numerical calculations, we only considered the sign-changing s-wave ($s_{\pm}$)

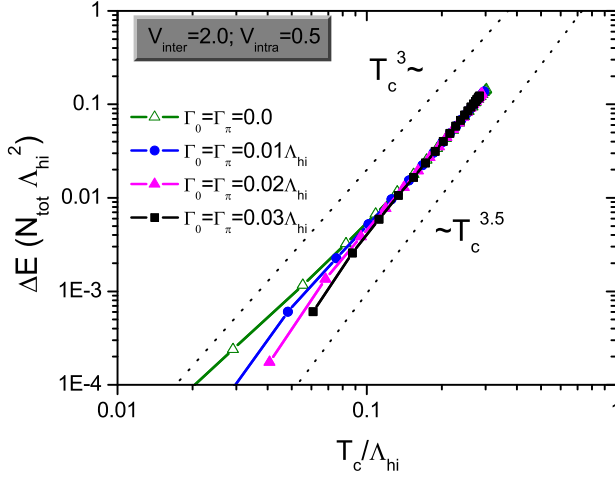


Fig. 3: (Color online) Numerical calculations of ΔE vs. T_c of the two band model with $\bar{V}_{inter} = 2.0$ and $\bar{V}_{intra} = 0.5$, with the pair-breaking impurity scattering rates Γ_π/Λ_{hi} are 0.0, 0.01, 0.02, and 0.03, respectively. The dotted lines of $\sim T_c^3$ and $\sim T_c^{3.5}$ are guides for the eyes.

gap solutions assuming a repulsive *inter-band* interaction ($V_{inter} > 0$). Also notice that all energy scales in this paper are normalized by N_{tot} such as $\bar{V}_{ab} = N_{tot}V_{ab}$ and $\bar{N}_{h,e} = N_{h,e}/N_{tot}$. For given pairing interactions $\bar{V}_{inter,intra}$, we solve the coupled gap equation Eq.(3) with the mean field Hamiltonian Eq.(2) for continuously varying $\bar{N}_h$ ($\bar{N}_e = 1 - \bar{N}_h$). In the $T \rightarrow 0$ limit, we obtain $\Delta_{h,e}$ and $b_{h,e}$ with which we can calculate ΔE with Eqs.(10) and (11). T_c can be calculated by taking $\Delta_{h,e} \rightarrow 0$ limit. ΔE is negative (< 0) by definition but we plot its absolute values in all figures.

In Fig.1, we studied the case of the pure inter-band pairing case (B): $\bar{V}_{intra} (= \bar{V}_{ee} = \bar{V}_{hh}) = 0$. We plotted ΔE vs. T_c for $\bar{V}_{inter} (= \bar{V}_{he} = \bar{V}_{eh}) = 1.0, 2.0, 3.0, 4.0$, and 5.0 , respectively. To our surprise, this simple model immediately produces a strongly non-BCS power law scaling $\Delta E \sim T_c^\beta$ ($\beta \approx 3$) for a wide range of T_c , and ΔE varies over three orders of magnitude. This is exactly the key feature of the experimental data. With the interaction strength $\bar{V}_{inter}$ used in Fig.1, the effective dimensionless coupling constant, $\lambda = \bar{V}_{inter}\sqrt{\bar{N}_h\bar{N}_e}$, runs from 0.3 to 2.5 ($\lambda_{min} = 1.0\sqrt{0.1 \times 0.9} = 0.3$ and $\lambda_{max} = 5.0\sqrt{0.5 \times 0.5} = 2.5$). Therefore it is clear that the strongly non-BCS power law behavior of Fig.1 is independent of the weak or strong coupling limits and is not an artifact of the strong coupling limit. Considering the extreme simplicity of two band model, we believe that this two-band model essentially captures the origin of the CE scaling behavior in the IBS, that is, a *multi-band BCS superconductor mediated by a dominant repulsive inter-band pairing interaction V_{inter}* .

As discussed with Eq.(9), when $\bar{V}_{intra} = 0$, the expression of the total CE ΔE appears as a sum of two single band BCS CE. Nevertheless, the result of Fig.1 shows that

it doesn't follow the standard BCS scaling law $\Delta E \sim T_c^2$ with $N_{tot} = const.$, but follows much stronger power law $\Delta E \sim T_c^\beta$ with $\beta \approx 3$, even for a very weak coupling limit of $\bar{V}_{inter} = 1.0$ ($0.3 < \lambda_{inter} < 0.5$). As we mentioned earlier, the origin of this strong power law is because of the combined effect of the unique inverse relation of $|\frac{\Delta_h}{\Delta_e}| \sim \frac{N_e}{N_h}$ and the T_c -equation $T_c \sim \exp[-1/(V_{inter}\sqrt{N_hN_e})]$ of the two band model in the pure inter-band pairing limit [4]. In fact, the results of Fig.1 can be exactly reproduced with an *attractive* inter-band pairing interaction ($\bar{V}_{inter} < 0$) with s_{++} -gap solution ($sign(\Delta_h) = sign(\Delta_e)$). However, we will find a consistent evidence to choose $\bar{V}_{inter} > 0$ when we consider the effect of the intra-band interaction $\bar{V}_{intra} \neq 0$ in Fig.2.

In Fig.2, we studied the effect of the intra-band interaction $\bar{V}_{intra} \neq 0$. We experimented both repulsive ($\bar{V}_{intra} > 0$) and attractive ($\bar{V}_{intra} < 0$) intra-band interactions while fixing the inter-band interaction $\bar{V}_{inter} = 2.0$ at a moderate value; in this case the effective dimensionless coupling constant $\lambda_{inter} = \bar{V}_{inter}\sqrt{\bar{N}_h\bar{N}_e}$ varies for $0.6 < \lambda_{inter} < 1.0$. First, when we add an attractive ($\bar{V}_{intra} < 0$) intra-band interaction, we found: (1) T_c quickly increases and the distribution of T_c s and ΔE s for varying $\bar{N}_h$ shrinks to the narrow range (see open pink stars for $\bar{V}_{intra} = -1.0$ and black solid squares for $\bar{V}_{intra} = -0.5$) of the upper right corner in Fig.2, which cannot be consistent with the three orders of magnitude variation of experimental data [2]. (2) Also the scaling power quickly converges to the BCS limit $\Delta E \sim T_c^2$ by even a very weak strength of the attractive intra-band interaction $\bar{V}_{intra} = -0.5$ (black solid squares). Again this cannot be compatible with experimental data. On the other hand, adding a repulsive intra-band interaction ($\bar{V}_{intra} > 0$), the opposite trend occurs, i.e., the scaling relation becomes steeper, in particular, more effective near the higher T_c region. However, this enhancement of scaling power is still weaker to fit the experimental data of $\Delta E \sim T_c^{3.5}$, and we need an addition mechanism to fit the data. Nevertheless, the important message of Fig.2 is that the intra-band interaction in the IBS should be repulsive ($\bar{V}_{intra} > 0$) – at least, not attractive.

Finally, in Fig.3, we studied the effect of the pair-breaking impurity scattering (interband impurity scattering) Γ_π ; the non-pair-breaking impurity scattering (intra-band impurity scattering) Γ_0 does not alter either T_c or $\Delta_{h,e}$, therefore has no effect on the scaling behavior. The physical non-magnetic impurities usually have both impurity potentials Γ_0 and Γ_π , and we considered in Fig.3 the maximum pair-breaking impurity, i.e. $\Gamma_0 = \Gamma_\pi$ [18]. The results in Fig.3 show that the scaling relation of ΔE vs. T_c very quickly becomes steeper with increasing the impurity scattering rate Γ_π . Even a very weak impurity scattering rate $\Gamma_\pi/\Lambda_{hi} = 0.03$ (black squares) is already sufficient to make the scaling as $\Delta E \sim T_c^{3.5}$ as consistent with the experimental data [2]. The technical reason why the impurity scattering Γ_π increases the scaling power as

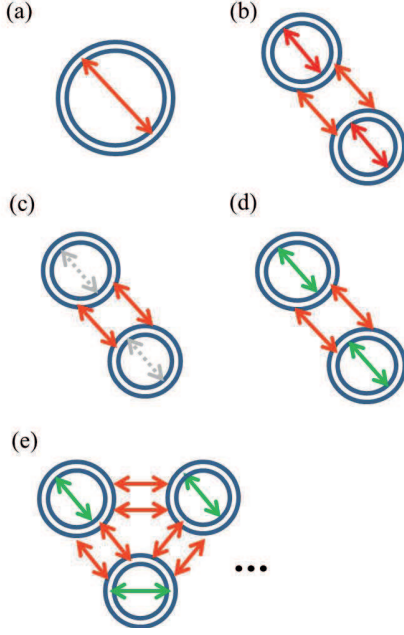


Fig. 4: (Color online) Illustrations of the KE losses and the PE gains with the SC ordering for a single- and multi-band systems. Double lined circles represent the FSs gapped by the SC ordering, hence the KE losses ($\Delta KE > 0$) are all equal for all cases with the same total DOS N_{tot} . However, the PE gains ($\Delta PE < 0$) differ in each case by the numbers of channels and the signs of the inter- and intra-band pairing interactions. (a) A single band system with only an attractive (red arrow, $V_{intra} < 0$) intra-band interaction (standard BCS case). (b) Two band system with both attractive (red) inter-band ($V_{inter} < 0$) and intra-band interactions ($V_{intra} < 0$); the total CE ΔE of this case is the same as (a). (c) Two band system with an attractive inter-band interactions ($V_{inter} < 0$) and zero (grey dotted, $V_{intra} = 0$) intra-band interactions. The intra-band part of the PE gain is lost in this case as $\Delta PE_{intra} = 0$. (d) Two band system with an attractive (red) inter-band interactions and repulsive (green) intra-band interactions. The PE gain is further reduced than (c) with $\Delta PE_{intra} > 0$. (e) N-band system with "N" repulsive (green) intra-band interactions and "N(N-1)" attractive (red) inter-band interactions.

shown in Fig.3 is due to the fact that in general the pair-breaking impurity scattering suppresses more efficiently the sizes of $\Delta_{h,e}$ than the size of T_c . The details of the impurity formalism is discussed in Appendix A.

General Principle determining the scaling power

β . – In Fig.1 and Fig.2, we have shown that the two band BCS model with dominant interband repulsion ($V_{inter} > V_{intra} > 0$) displays the anomalous scaling relation $\Delta E \sim T_c^\beta$, ($\beta \approx 3$) as a generic feature of the multi-band superconductor. We also found that the repulsive (attractive) intra-band interactions V_{intra} increases (decreases) the scaling power β . We would like to discuss this effect of the intra-band interaction, $V_{intra} > 0$ or < 0 , on the scaling power β in a more general context. In the introduction,

we have pointed out that the PE only transition such as insulating magnets has $\Delta E \sim T_c$, while the BCS superconductor which develops the transition by a subtle balance between the ΔPE and ΔKE has $\Delta E \sim T_c^2$. This balance between the ΔKE loss (> 0) and the ΔPE gain (< 0) is the generic feature of the ordering transitions of the itinerant fermion system such as superconductivity and density wave (DW) transitions. In this view, the higher power scaling relation $\Delta E \sim T_c^{3.5}$ observed in the IBS [2] implies that the Fe-based superconductivity should be: either (1) suffering more KE loss, and/or (2) not sufficiently harvesting the PE gain through its transition. Both cases are not good news for us wishing the maximum gain of CE in order to increase T_c . We will show below that the cause (2) is the fundamental origin of the steeper scaling relation ($\Delta E \sim T_c^{3.5}$) of the IBS.

In Fig.4, we illustrate this energetic balance of the multi-band SC systems. For a convenience of illustrations, we consider "attractive" inter-band interaction ($V_{inter} < 0$, red color) with the Δ_{++} gap solution in Fig.4. Energetics-wise, this is exactly the same as the "repulsive" inter-band interaction ($V_{inter} > 0$) with the $\Delta_{\pm}$ gap solution. With this assumption, we can systematically discuss the continuous evolution of energetics, starting from the single band BCS superconductor to multi-band systems.

Within the BCS theory, when FS opens a gap Δ_i , the KE increase (KE loss) in each band "i" has always the same form as

$$\Delta KE_i = -\frac{1}{2}N_i\Delta_i^2 + N_i\Delta_i^2 \log \frac{\Lambda_{hi} + \sqrt{\Lambda_{hi}^2 + \Delta_i^2}}{|\Delta_i|} \quad (12)$$

where N_i is the DOS and Δ_i is the gap of the i th band. This form of ΔKE doesn't change with the number of bands, and therefore assuming $N_{tot} = \sum_i N_i = const.$, the total KE loss ΔKE should be approximately the same size, depending on the average value of Δ_i , regardless of the number of bands. On the other hand, the PE gain ($\Delta PE < 0$) of the multi-band systems differs by the numbers of the channels and signs of the inter- and intra-band pairing interactions, respectively.

Fig.4(a) is the case of a single band BCS superconductor with only an attractive (red arrow, $V_{intra} < 0$) intra-band interaction. This system obtains the maximum PE gain $\frac{\Delta^2}{V_{intra}}$. Combining the KE loss of Eq.(12), the total CE becomes $\Delta E_{(a)} = -\frac{1}{2}N_0\Delta^2$, which is $\sim T_c^2$. Fig.4(b) is the two band system with both attractive (red) inter-band ($V_{inter} < 0$) and intra-band interactions ($V_{intra} < 0$). If the strengths of the interactions are the same as $V_{inter} = V_{intra}$, this system is mathematically the same as the single band system Fig.4(a). Hence we would get $\Delta E_{(b)} \sim T_c^2$. Fig.4(c) is the two band system with attractive (red) inter-band interactions ($V_{inter} < 0$) and zero (grey dotted, $V_{intra} = 0$) intra-band interactions. Compared to (b), the case (c) apparently loses the "intra-part" of the PE gain ($\Delta PE_{intra} = 0$). And we found with the numerical calculations in Fig.1 that $\Delta E_{(c)} \sim T_c^\beta$ with

$\beta \approx 3$. Namely, the scaling power β has increased from the standard BCS value $\beta_{BCS} = 2$ because of the loss of the "intra-part" of the PE gain compared to the case (b).

Fig.4(d) has a repulsive (green) intra-band interactions ($V_{inter} > 0$). Compared to the cases (b) and (c), now $\Delta PE_{intra} (> 0)$ becomes not a gain but a loss. Hence we can expect that the scaling power β further increase and that is indeed confirmed by the numerical calculations in Fig.2. These case studies of (b), (c), and (d) tell us that the intra-band interaction V_{intra} in the real compounds of the IBS cannot be attractive but likely to be weakly repulsive as depicted in Fig.4(d). And all our discussions of the KE losses and the PE gains in Fig.4(b), (c), and (d) are unchanged if we replace the "attractive" inter-band interaction $V_{inter} (< 0)$ by the "repulsive" inter-band interaction $V_{inter} (> 0)$, and the Δ_{++} gap – assumed in this discussion – by the $\Delta_{\pm}$ gap, so that now Fig.4(d) has all repulsive interactions $V(\mathbf{q}) > 0$, which is consistent with the spin-fluctuation mediated interaction scenarios [19–21].

Finally, although physically not realistic but for a mathematical completeness, we considered a N -band limit in Fig.4(e). In this case, the number of repulsive intra-band interaction channels increases as $\sim N$ and the number of attractive inter-band interaction channels increases as $\sim N(N-1)$. In large- N limit, the inter-band interaction channels dominate over the intra-band channels and as a result the energetics of the system converges back to the single band BCS limit; this N -band system can be equivalently viewed as a N -sectioned single Fermi pocket system. This analysis of a unphysical system, however, tells us that the *two band system with a repulsive intra-band interaction is the case with the maximum loss of ΔPE_{intra} , and therefore has the maximum scaling power $\beta_{Max} \approx 3$* , unless other extrinsic effects such as a pair-breaking impurity effect further increases it.

Strong coupling effects. – Our study, being a mean field theory, didn't include the dynamical effects of the strong coupling theory such as Eliashberg theory. In particular, Dolgov *et al.* [22] have shown that the strong coupling effects, by inducing the mass-renormalization, qualitatively changes the relation between Δ_h/Δ_e vs. N_e/N_h from the weak coupling (BCS) theory that we used in this paper. However, this renormalization effect can be completely absorbed into our weak coupling formalism by replacing $N_{h(e)}$ in our theory with $\tilde{N}_{h(e)} = N_{h(e)}/[1 + V_{inter}N_{h(e)}]$ [23]. Therefore, as far as the implicit parameter $R = \tilde{N}_h/\tilde{N}_e$ – although it is reduced compared to $R_0 = N_h/N_e$ – can vary in a substantial range of $[0, 1]$, all the scaling results in this paper remain unchanged. As a result, the basic energetics (the KE loss and the PE gain) of the multiband BCS superconductor and its scaling relation of ΔE vs. T_c , should be generic and robust regardless of the weak or strong coupling limit.

Summary and Conclusions. – We have studied the scaling relation of the ΔE vs. T_c of the two band BCS

model. The doping (either holes or electrons) in the real IBS compounds was modeled by continuously varying the hole (N_h) and electron (N_e) DOSs keeping the total DOS $N_{tot} = const.$ With numerical calculations, we found: (1) $\Delta E \sim T_c^\beta$ with $\beta \approx 3$ is a generic feature of the two band BCS superconductor with a dominant inter-band pairing interaction (either attractive or repulsive). (2) A repulsive intra-band interaction tends to increase the scaling power β . On the other hand, an attractive intra-band interaction, even if very weak, immediately turns the scaling power into a BCS limit $\Delta E \sim T_c^2$. Therefore we are forced to rule out a possible attractive intra-band interaction in real compounds. (3) Adding a small amount of pair-breaking impurity scattering ($\Gamma_\pi = 0.05\Lambda_{hi}$) can easily increase β close to the experimental value of $\beta_{exp} \approx 3.5$.

We have also illustrated that the general principle determining the scaling relation $\Delta E \sim T_c^\beta$ is the balance between the KE loss and the PE gain through the SC transition. The origin of the stronger scaling power of $\Delta E \sim T_c^\beta$ ($\beta \approx 3$) than the standard BCS scaling of $\beta_{BCS} = 2$ is due to the fact that the IBS, being a multi-band BCS superconductor, didn't fully harvest all possible PE gain, specifically, losing the intra-band PE part ($\Delta PE_{intra} > 0$) because of the repulsive V_{intra} .

In conclusion, our study implies that the experimentally observed seemingly non-BCS scaling relation of $\Delta E \sim T_c^{3.5}$ [2] is in fact a strong experimental evidence that the IBS are the BCS superconductors, but with multi-bands, mediated by a dominant repulsive inter-band pairing interaction. All strong correlation effects, abundantly observed in the normal state, should renormalize the effective mass m_{qp}^* of quasiparticles, DOS $N_{h,e}$, pairing interactions $V_{inter,intra}(\mathbf{q})$, etc., but when the system enters the SC transition, the pairing mechanism itself seems to be governed by the BCS mechanism. Finally, the results of this paper has no direct relevance to the FeSe monolayer and related systems where only electron FSs exist [24].

This work was supported by Chonnam National University Grant 2014 and NRF Grant 2013-R1A1A2-057535 funded by the National Research Foundation of Korea. The author gratefully acknowledge insightful discussions with G. R. Stewart.

Appendix A: Impurity scattering formalism. – In this paper, we only consider the non-magnetic impurities, and for our two band BCS model, the non-magnetic impurity scattering process can be conveniently described by two impurity scattering rate parameters: Γ_0 (intra-band) and Γ_π (inter-band). And all impurity scattering effects enter the coupled gap equations Eq.(3) in the main text through the pair susceptibilities $\chi_{h,e}$, which is defined as follows.

$$b^{h(e)} = \sum_k b_k^{h(e)} = \Delta_{h(e)} \chi_{h,e}(T), \quad (A1)$$

with $b_k^h = \langle h_{k\uparrow} h_{-k\downarrow} \rangle$ and $b_k^e = \langle e_{k\uparrow} e_{-k\downarrow} \rangle$, respectively. Without impurities, these pair susceptibilities $\chi_{h,e}(T)$ can be analytically calculated in BCS limit, but with impurities they need numerical calculations with the following expression,

$$\chi_{h,e}(T) = T \sum_n N_{h,e} \int_{-\Lambda_{sf}}^{\Lambda_{sf}} d\xi \frac{\delta_{h,e}}{\tilde{\omega}_n^2 + \xi^2 + \tilde{\Delta}_{h,e}^2}. \quad (\text{A2})$$

where $\tilde{\omega}_n = \omega_n + (\Gamma_0 + \Gamma_\pi)$ is the renormalized Matsubara frequency by the non-magnetic impurity scattering, and conveniently parameterized as $\tilde{\omega}_n = \omega_n \eta_0$ with $\eta_0 = 1 + (\Gamma_0 + \Gamma_\pi)/|\omega_n|$. $\delta_{h,e}$ are the renormalization parameter of the OPs $\Delta_{h,e}$ due to impurities, which is defined as $\delta_{h,e} = 1 + (\Gamma_0 + a_{h,e} \Gamma_\pi)/|\omega_n|$, with $a_h = \frac{(N_e \Delta_e)}{(N_h \Delta_h)}$ and $a_e = \frac{(N_h \Delta_h)}{(N_e \Delta_e)}$; $a_{h,e}$ are always negative number, because of the opposite signs of Δ_h and Δ_e , and its size is $\sim O(1)$ [18]; and if $\Gamma_0 = \Gamma_\pi$, $\delta_{h,e} \approx 1$. We can clearly see that Γ_0 alone does not affect T_c and $\Delta_{h,e}$, because when $\Gamma_\pi = 0$ and $\Gamma_0 \neq 0$, then $\eta_0 = \delta_{h,e}$, and in this case the pair susceptibilities $\chi_{h,e}(T)$ are not renormalized with impurities [25, 26]; therefore, only Γ_π is pair-breaking [18]. In this paper, we considered the maximum pair-breaking non-magnetic impurities, i.e., $\Gamma_0 = \Gamma_\pi$, and in this case $\delta_{h,e} \approx 1$.

Regarding the systematic enhancement of the scaling power in $\Delta E \sim T_c^\beta$ with impurity scattering $\Gamma_0 = \Gamma_\pi \neq 0$ in Fig.3 in the main text, we argued that its origin is because the impurity suppression rate of OPs $\tilde{\Delta}_{h,e}$ is faster than the impurity suppression rate of T_c . To see this, the T_c -suppression is determined by $\chi_{h,e}(T = T_c)$,

$$\chi_{h,e}(T_c) \approx T_c \sum_n N_{h,e} \int_{-\Lambda_{sf}}^{\Lambda_{sf}} d\xi \frac{1}{(\omega_n \eta_0)^2 + \xi^2}. \quad (\text{A3})$$

With the above renormalized susceptibility, we can read that T_c is reduced in linear with Γ_π as $T_c \approx T_c^0 - \frac{\pi}{4} \Gamma_\pi$ [26]. On the other hand, the $\Delta_{h,e}$ -suppression is determined by $\chi_{h,e}(T \rightarrow 0)$ as

$$\chi_{h,e}(T \rightarrow 0) \approx T \sum_n N_{h,e} \int_{-\Lambda_{sf}}^{\Lambda_{sf}} d\xi \frac{1}{(\omega_n \eta_0)^2 + \xi^2 + \tilde{\Delta}_{h,e}^2}. \quad (\text{A4})$$

When the above susceptibilities are substituted into the gap equations Eq.(3) in the main text, it is clear that the renormalized $\tilde{\Delta}_{h,e}$ are determined by the non-linear equations, and this non-linear suppression of $\tilde{\Delta}_{h,e}$ is systematically enhanced as $\tilde{\Delta}_{h,e}$ become smaller values, as seen in the lower-left corner region in Fig.3. As results of all these effects, Fig.3 shows that the low T_c tail of the ΔE vs. T_c scaling becomes systematically steeper with impurity scattering.

REFERENCES

- [1] J. BARDEEN, L. N. COOPER, and J. R. SCHRIEFFER, *Phys. Rev.*, **108** (1957) 1175.
- [2] J. XING ET AL., *Phys. Rev. B*, **89** (2014) 140503(R).
- [3] J. ZAAENEN, *Phys. Rev. B*, **80** (2009) 212502(R).
- [4] Y. BANG and G. R. STEWART, *New J. Phys.*, **18** (2016) 023017.
- [5] S. L. BUD'KO, N. NI, and P. C. CANFIELD, *Phys. Rev. B*, **79** (2009) 220516.
- [6] S. L. BUD'KO, M. STURZA, D. Y. CHUNG, M. G. KANATZIDIS, and P. C. CANFIELD, *Phys. Rev. B*, **87** (2013) 100509.
- [7] S. L. BUD'KO, D. Y. CHUNG, D. BUGARIS, H. CLAUS, M. G. KANATZIDIS, and P. C. CANFIELD, *Phys. Rev. B*, **89** (2014) 014510.
- [8] J. S. KIM, G. R. STEWART, S. KASAHARA, T. SHIBAUCHI, T. TERASHIMA, and Y. MATSUDA, *J. Phys.: Condens. Matter*, **23** (2011) 222201.
- [9] J. S. KIM, B. D. FAETH, and G. R. STEWART, *Phys. Rev. B*, **86** (2012) 054509.
- [10] F. HARDY ET AL., *Phys. Rev. B*, **81** (2010) 060501(R).
- [11] F. HARDY ET AL., *Europhys. Lett.*, **91** (2010) 47008.
- [12] K. GOFRYK ET AL., *Phys. Rev. B*, **81** (2010) 184518.
- [13] K. GOFRYK ET AL., *Phys. Rev. B*, **83** (2011) 064513.
- [14] Y. BANG and H.-Y. CHOI, *Phys. Rev. B*, **78** (2008) 134523.
- [15] M. TINKHAM, *Introduction to Superconductivity* (2nd edit.) (McGraw-Hill, Inc.) 1996, p. 57.
- [16] T. SATO ET AL., *Phys. Rev. Lett.*, **103** (2009) 047002.
- [17] T. SUDAYAMA ET AL., *Phys. Rev. Lett.*, **104** (2010) 177002.
- [18] Y. BANG, H.-Y. CHOI, and H. WON, *Phys. Rev. B*, **79** (2009) 54529.
- [19] I. I. MAZIN, D. J. SINGH, M. D. JOHANNES, and M.H. DU, *Phys. Rev. Lett.*, **101** (2008) 057003.
- [20] K. KUROKI, S. ONARI, R. ARITA, H. USUI, Y. TANAKA, H. KONTANI, and H. AOKI, *Phys. Rev. Lett.*, **101** (2008) 087004.
- [21] A. V. CHUBUKOV and P.J. HIRSCHFELD, *Physics Today*, **68** (2015) 46.
- [22] O. V. DOLGOV, I. I. MAZIN, D. PARKER and A. A. GOLUBOV, *Phys. Rev. B*, **79** (2009) 060502 (R).
- [23] These redefined DOSs $\tilde{N}_{h(e)} = N_{h(e)}/[1 + V_{inter}N_{h(e)}]$ are not the commonly defined (physical) renormalized DOSs, which are rather $\tilde{N}_{h(e)}^{phy} = N_{h(e)} \cdot [1 + V_{inter}N_{e(h)}]$.
- [24] Q. Y. WANG ET AL., *Chin. Phys. Lett.*, **29** (2012) 37402.
- [25] P. W. ANDERSON, *J. Phys. Chem. Solids*, **11** (1959) 26.
- [26] A. A. ABRIKOSOV and L. P. GORKOV, *Sov. Phys. JETP*, **12** (1961) 1243.